



Response of fly ash-bentonite based landfill liner to chemical solutions

G Suneel Kumar¹, Ede Lakshmi Suresh Babu² and Rabi Narayan Behera^{3*}

¹ Ph.D. Student, Department of Civil Engineering, National Institute of Technology Rourkela, Odisha, India, 769008.

² M.Tech Student, Department of Civil Engineering, National Institute of Technology Rourkela, Odisha, India, 769008.

³ Assistant Professor, Department of Civil Engineering, National Institute of Technology Rourkela, Odisha, India, 769008.

* e-mail: rnbehera82@gmail.com

Introduction

Hydraulic barriers are a part of lining systems which are responsible for preventing a potential pollutant present in the waste containment from migrating to surface water, groundwater and thus polluting them. Natural clays, calcium or sodium-based bentonite mixed with specific geo-materials are widely used in the construction of hydraulic barriers such as liners and covers due to their low hydraulic conductivity (i.e. $k \leq 10^{-7}$ cm/sec). However, the long term interaction of landfill liner with leachate leads to the change in its permeability. Thus, addressing the need to study the interaction of leachate with liner material.

In the present study, Sodium bentonite (low sodium content) instead of calcium bentonite was used as the hydraulic conductivity of Na-bentonite is approximately five times lower than that of the Ca-bentonite at similar void ratios (Mesri and Olson 1971). Chlorides and Sulphates are widely distributed in nature and are common constituents in the leachate (Arasan and Yetimoglu 2006; Yilmaz et al. 2008), the chemical properties of the landfill leachate listed by Kayabali et al. 1998, also showed larger amounts of Cl^- , Na^+ , K^+ ions which are exchangeable. Therefore, chlorides and sulphates of different cations such as Sodium, Calcium, and Iron etc. are chosen for the permeation process, which best represents the in-situ conditions in the laboratory. The preference for replacement is the lyotropic series, which is Li^+ , Na^+ , K^+ , Rb^+ , Cs^+ , Mg^{2+} , Ca^{2+} , Ba^{2+} , Cu^{2+} , Al^{3+} , Fe^{3+} (Sposito 1981; McBride 1994). Because Na^+ is at the lower end of the lyotropic series, Na-bentonites are more prone to cation exchange when permeated with solutions containing divalent or trivalent ions (Sposito 1981).

Therefore, in the present study, bentonite mixed with fly ash (FA-B) was permeated with different chemical solutions and their chemical compatibility as a liner material was assessed.

Materials and Methodology

Cohesionless material includes Fly ash collected from Aditya Alumina Ltd. situated in Lapanga town of Sambalpur district, Odisha. Cohesive material includes commercially available sodium based bentonite in the local market.

The basic geotechnical characteristics of the materials were found out by performing different laboratory tests (Table 1). In order to assess the chemical characteristics, permeability tests are carried out using a pressure-permeameter, under different heads of 15m, 25m, 35m and 45m of water respectively, on different trial mixes of fly ash and bentonite with different chemicals.

The bentonite content in the fly ash-bentonite mixture is taken up to 15% @ 5% increment starting from 5%. The permeant solutions used include NaCl, NaOH, HCl, CaCl_2 , H_2SO_4 , and FeCl_3 , which are chosen to best represent the acidic, basic, neutral nature of the landfill leachate as well as to better portray the effect of monovalent, divalent, trivalent cations present in the in-situ landfill leachate.

Results and Concluding Remarks

Table 1. Geotechnical properties of fly ash and bentonite

Property	Fly ash	Bentonite
Specific Gravity	2.08	2.74
Liquid limit, LL (%)	-	268
Plastic limit, PL (%)	-	54
Linear Shrinkage, L_s	-	29

Plasticity Index, <i>PI</i> (%)	-	214
Differential Free Swell Index, <i>DFSI</i> (%)	0	400

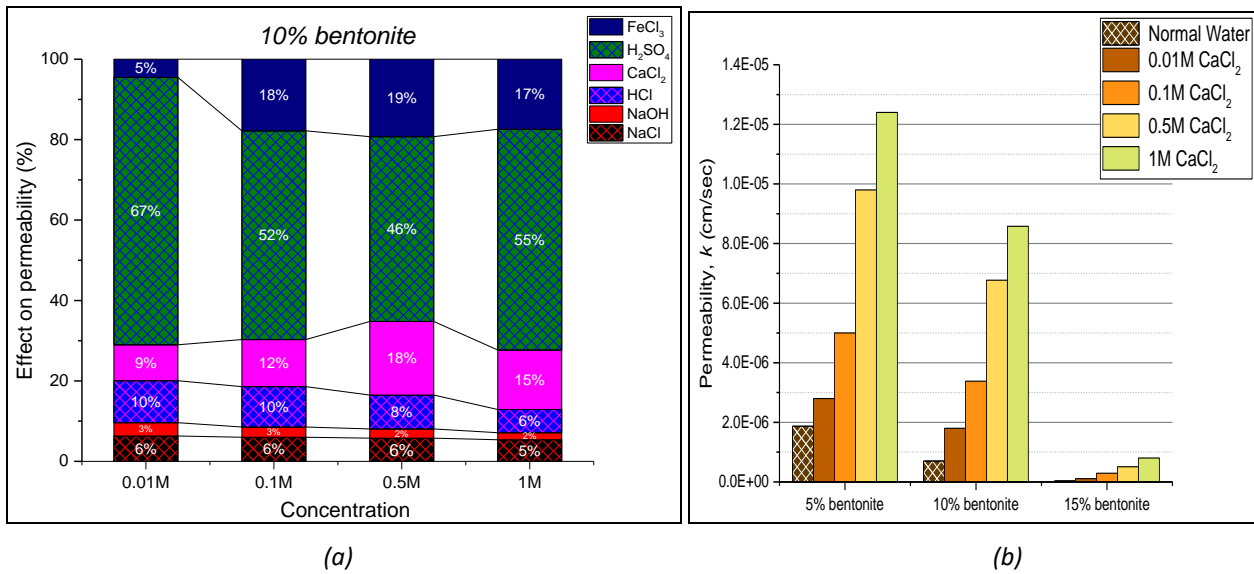


Figure 2. (a) Effect of concentration and type of permeant solution on permeability of FA-B mixture for 10% bentonite
(b) Effect of bentonite content and CaCl₂ concentration on permeability of FA-B mixture

The basic criteria to be fulfilled by a liner material include the strength criteria ($\geq 0.2\text{MPa}$) and the permeability criteria ($k \leq 10^{-7}$ cm/sec). Based on the test results of fly ash and bentonite mixtures (i.e. 85:15, 90:10 and 95:05) with six types of permeating solutions (i.e. NaCl, NaOH, HCl, CaCl₂, H₂SO₄ and FeCl₃) of five different concentrations (i.e. 0, 0.01M, 0.1M, 0.5M and 1M), the following major inferences were drawn. However, the strength characteristics of FA-B mixtures as assessed by Alla et al. 2017 increases with the ageing of liner material due to increasing overburden. Therefore, the permeability characteristics were given priority in this work.

- Irrespective of the nature of the permeant solution (acidic/basic/neutral), the hydraulic conductivity of all the fly ash-bentonite mixtures increased with an increase in chemical concentrations (Figure 2(b)).
- The net repulsive forces were better suppressed by multivalent ions than the monovalent ions, resulting in the flocculation of bentonite particles leading to higher permeability (Figure 2(a)).
- The effect of valence of cation is more at higher concentrations than at lower concentrations i.e., with increase in cation valence the hydraulic conductivity increases and has negligible effect when solutions were dilute ($\leq 0.01\text{M}$).

References

- Alla V, Sasmal SK, Behera RN, Patra CR. Development of alternate liner material by blending fly ash, local soil and bentonite. In: Proceedings of Indian Geotechnical Conference GeoNEst, 14-16 December 2017, IIT Guwahati, India, 95
- Arasan S, Yetimoglu T (2006) Effect of leachate components on the consistency limits of clay liners. In: 11th National Soil Mechanics and Foundation Engineering Congress, Trabzon, Turkey (pp. 439-445)
- Kayabali K, Kezer H (1998) Testing the ability of bentonite-amended natural zeolite (clinoptinolite) to remove heavy metals from liquid waste. *Environmental Geology* 34(2-3):95-102
- McBride MB. *Environmental chemistry of soils*. Oxford University Press. New York; 1994.
- Mesri G, Olson RE (1971) Mechanisms controlling the permeability of clays. *Clays and Clay Minerals* 19:151-158
- Sposito G. *The thermodynamics of soil solutions*. Oxford University Press; 1981.
- Yilmaz G, Yetimoglu T, Arasan S (2008) Hydraulic conductivity of compacted clay liners permeated with inorganic salt solutions. *Waste Management & Research* 26(5):464-473